

## 1. Description

Valchromat is a panel made of wood fibres coloured in the production process. The fibres are impregnated with organic colouring agents and chemically bound to one another by a special resin which lends Valchromat unique physicochemical features. Valchromat is an MDF.HLS, in compliance with the EN 622-5 standard.

Valchromat panels, thanks to the use of organic colouring agents and the natural variation of the wood colour, come in different shades. This variation may be seen on the same surface, between the two faces of the same panel, or between the different production batches or thicknesses. To minimize this effect, the supply must be from a single production.

Valchromat is a moisture resistant panel, supplied with no finish, and therefore a layer of varnish, wax or oil is recommended.

## 2. Colours



WP - White Pearl

WG - White Grey

LG - Light Grey

CZ - Grey

LB - Black

CB - Chocolate



SC - Red

YW - Yellow

OR - Orange

RB - Blue

GM - Green Mint

CQ - Khaki

## 3. Applications

Interior design, furniture, linings, flooring, doors, bathrooms and kitchens, restaurants, exhibition stands, shopfitting, decorative panels, acoustic panels, among others.

Whenever the panels are used in moist zones, such as bathrooms or kitchens, it should be protected with a varnish and the edges must be properly sealed.

The Valchromat panels should not be applied in places where they will come into direct contact with water, such as kitchen worktops and bathroom showers.

## 4. Dimensions

2440 x 1220, 2440 x 1830, 3660 x 1220 e 3660 x 2440 [mm]

96 x 48, 96 x 72, 144 x 48, 144 x 96 [inch]

## 5. Thicknesses

8, 12, 16, 19 and 30 [mm]

5/16, 1/2, 5/8, 3/4 and 1 3/16 [inch]

## 6. Thickness and cutting tolerances

Characteristics	Thickness				
	8 mm 5/16"	12 mm 1/2"	16 mm 5/8"	19 mm 3/4"	30 mm 1 3/16
Thickness tolerance	±0,2 mm ±0.008"				±0,3 mm ±0.012"
Cutting tolerance	± 2 mm/m; maximum of 5 mm 0.2%; maximum of 0.22"				

## 7. Finishes

A finish should be applied to the Valchromat panel to protect its surface and maintain its appearance. The finish can be varnish, wax or oil.

### Varnish

- Of the three kinds of finishes described, the varnishes are the most complex and at times the most difficult to choose given the broad range available on the market. Any wood varnish can be applied to Valchromat.
- Varnishes manufactured with acrylic resins and aliphatic polyurethane are widely used, since they do not yellow over time. The water-based varnishes change the natural colour of the panel less.
- When a varnish finish is applied, the first coat applied is a primer. After the primer has dried, the panel should be sanded with fine sandpaper with grit size 320-360, to remove the granules that may result from peeling.
- Next, a varnish finish is applied in one or two coats, in line with the manufacturer's instructions. Between each layer the panel should be sanded using fine sandpaper with grit size 320-360.
- There are different varnishes with different appearances, from matt to gloss.
- Primer and the varnish from the same manufacturer should be used to avoid incompatibility between them.

### Waxes and oils

- These kinds of finishes should not be applied on panels for installation in moist environments, such as kitchens and bathrooms.
- Some types of waxes and oils, such as beeswax and linseed oil, can stain the panel, so these products are not recommended. Acrylic waxes and mineral oils are widely used.

### Surface preparation

- Given that there will be a difference in shades of the panels from the same batch, before installing them, the panels should be laid out side by side and ordered so as to minimise these differences in adjacent panels.
- In general, any finish, be it varnish, wax or oil, needs the surface to be prepared beforehand. This preparation involves sanding the surfaces before applying the finish.
- Depending on the type of finish the panel will receive, different types of sandpaper grains may be recommended. It is common to prepare the surface with 150/180 grit sandpaper.
- If a finer sandpaper is required, the process should be gradual, increasing the sandpaper grain by 50% at each new step. Edges should be treated equally.
- Valchromat panels are factory-sanded to 150 grits for 19 and 30 mm thicknesses, and 180 grit for 8, 12 and 16 mm thicknesses.
- Before applying the finish, the panels must be cleaned with a dry cloth, air blowing or, preferably with a vacuum cleaner to be free of any type of dust, which will damage the finish.

## 8. Certifications

Valbopan S.A. complies with the requirements of the EN ISO 9001 Standard.

Valchromat is certified through CE 1328-CPR-0062, complying with the requirements of the EN 13986 standard.

Valbopan S.A. holds the Chain of Custody Certification, in accordance with the applicable normative references.

Upon request, the Valchromat panel can be supplied with one of the FSC® C101993 or PEFC/13-31-027 certifications.

Upon request Valchromat can be supplied with CARB Phase 2 or US EPA-TSCS Title VI certification.


### 9. Panel weight

Thickness	8 mm 5/16"	12 mm 1/2"	16 mm 5/8"	19 mm 3/4"	30 mm 1 3/16"
Weight per sqm	6.6 Kg/m <sup>2</sup> 1.36 psf	9.6 Kg/m <sup>2</sup> 1.97 psf	12.5 Kg/m <sup>2</sup> 2.56 psf	14.6 Kg/m <sup>2</sup> 3.00 psf	21.6 Kg/m <sup>2</sup> 4.42psf
<b>Panel weight (kg)</b>					
2440 x 1220 mm 96" x 48"	19.8 Kg 43.3 Lb	28.6 Kg 63.0 Lb	37.2 Kg 81.9 Lb	43.6 Kg 96.0 Lb	64.3 Kg 141.8 Lb
2440 x 1830 mm 96" x 72"	29.6 Kg 65.4 Lb	42.9 Kg 94.5 Lb	55.7 Kg 122.9 Lb	65.3 Kg 144.0 Lb	96.4 Kg 212.6 Lb
3660 x 1220 mm 144" x 48"	29.6 Kg 65.4 Lb	42.9 Kg 94.5 Lb	55.7 Kg 122.9 Lb	65.3 Kg 144.0 Lb	96.4 Kg 212.6 Lb
3660 x 2440 mm 144" x 96"	59.3 Kg 130.7 Lb	85.7 Kg 189.0 Lb	111.5 Kg 245.7 Lb	130.7 Kg 288.0 Lb	192.9 Kg 425.3 Lb

### 10. Storage

Valchromat panels must be stored in a closed area, protected from sunlight, with controlled temperature and humidity, supported on a flat and horizontal base. The pallets must be placed on supports with sufficient height to allow easy access with a forklift. The maximum distance between supports should not exceed 800 mm.

If the pallets are piled on top of each other, all the support bases must be aligned to prevent deformation.

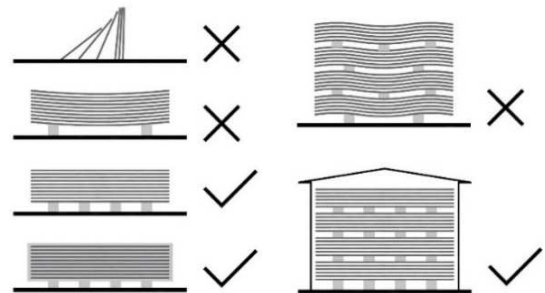

### 11. Handling

Whenever possible, the handling of the panels should be performed using appropriate equipment, such as forklifts or plate lifts.

When the panels must be moved manually, they must be moved one by one, in the vertical position, in order to remain flat and without deforming, their movement should not be performed without sufficient people being present.

Good manual handling practices should be followed, using the appropriate personal protective equipment and following the rules of European Health and Safety legislation.



**12. Properties**

Characteristics	Units	Thickness (mm)					Norma
	mm	8	12	16	19	30	
	inch	5/16	1/2	5/8	3/4	1 3/16	
Density	Kg/m <sup>3</sup>	830	800	780	770	720	EN 323
	Lb/ft <sup>3</sup>	51.8	49.9	48.7	48.1	44.9	
Bending Strength	N/mm <sup>2</sup>	42	40	38	38	36	EN 310
	psi	6100	5800	5500	5500	5200	
Modulus of Elasticity in bending	N/mm <sup>2</sup>	3400	3200	3100	3100	3000	EN 310
	psi	493000	464000	449600	449600	435000	
Internal Bond	N/mm <sup>2</sup>	0.80	0.80	0.75	0.75	0.75	EN 319
	psi	116	116	109	109	109	
Swelling in thickness 24h	%	12	10	8	8	7	EN 317
Internal Bond after Cyclic Test	N/mm <sup>2</sup>	0.30	0.25	0.20	0.20	0.15	EN 321
	psi	44	36	29	29	22	
Swelling in thickness after Cyclic Test	%	19	16	15	15	15	EN 321
Formaldehyde content	-	≤ 8 mg/100g, Classe E1					EN ISO 12460-5
Fire Reaction	-	F	D-s2,d0			EN 13501	